

SF-80W

FLUX CORED ARC WELDING CONSUMABLES
FOR ATMOSPHERIC CORROSION RESISTING STEEL

2022.02

HYUNDAI WELDING CO., LTD.



❖ Specification

<i>AWS A5.29</i>	E81T1-W2C
<i>(AWS A5.29M</i>	E551T1-W2C)
<i>EN ISO 17632-B</i>	T55 3 T1-1 C1 A-NCC1
<i>JIS Z 3320</i>	T55 3 T1-1 C A-NCC1 H10

❖ Applications

All position welding of bridges, building using atmospheric corrosion resisting steels.

❖ Characteristics on Usage

SF-80W is the most widely used titania type flux cored wire for all position welding with CO₂ shielding gas. Arc stability is excellent, so spatter loss is low and slag covering is uniform with good removability. SF-80W is effective for use in insufficient ventilation and/or space areas.

❖ Note on Usage


1. For preheating guidelines, please refer to your local standards and codes relative to your best practices
2. One-side welding defects such as hot cracking may occur with wrong welding parameter such as high welding speed.
3. Use 100% CO₂ gas.



Mechanical Properties & Chemical Composition of All Weld Metal

❖ Welding Conditions

Method by AWS Spec.

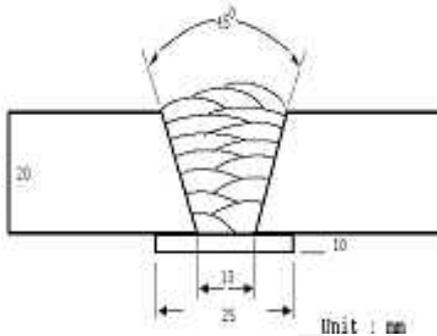

[Joint Preparation & Layer Details]

Welding Position	: 1G(PA)
Diameter	: 1.2mm (0.045in)
Shielding Gas	: 100%CO ₂
Flow Rate	: 20 ℓ /min
Amp./ Volt.	: 280A / 32V
Stick-Out	: 20~25mm (0.79~0.98in)
Pre-Heat	: R.T .
Interpass Temp.	: 150±15℃ (302±59°F)
Polarity	: DC(+)

❖ Mechanical Properties of all weld metal

Consumable	Tensile Test			CVN Impact Test J(ft · lbs)	
	YS MPa (lbs/in ²)	TS MPa (lbs/in ²)	EL (%)	-18℃ (0°F)	-29℃ (-20°F)
SF-80W	540 (75,000)	615 (84,000)	28.0	66 (49)	46 (34)
AWS A5.29 E81T1-W2C	≥ 470 (68,000)	550~690 (80,000~ 100,000)	≥ 22.0	≥ 27J at -29℃ (≥ 20ft · lbs at -20°F)	

❖ Chemical Analysis of all weld metal(wt%)

Consumable	C	Si	Mn	P	S	Cu	Cr	Ni
SF-80W	0.04	0.40	0.92	0.016	0.009	0.40	0.52	0.50
AWS A5.29 E81T1-W2C	≤ 0.12	0.35~0.80	0.50~1.30	≤ 0.03	≤ 0.03	0.30~0.75	0.45~0.70	0.40~0.80


This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



Mechanical Properties & Chemical Composition of All Weld Metal

❖ Welding Conditions

Method by AWS Spec.

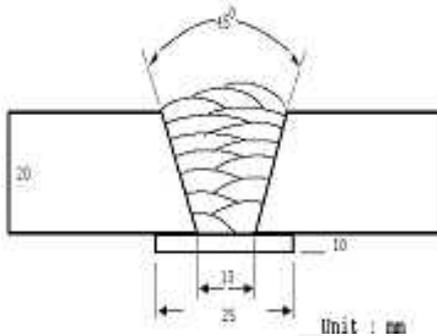

[Joint Preparation & Layer Details]

Welding Position	: 1G(PA)
Diameter	: 1.4mm (0.052in)
Shielding Gas	: 100%CO ₂
Flow Rate	: 20 ℓ /min
Amp./ Volt.	: 300A / 32V
Stick-Out	: 20~25mm (0.79~0.98in)
Pre-Heat	: R.T .
Interpass Temp.	: 150±15°C (302±59°F)
Polarity	: DC(+)

❖ Mechanical Properties of all weld metal

Consumable	Tensile Test			CVN Impact Test J(ft · lbs)	
	YS MPa (lbs/in ²)	TS MPa (lbs/in ²)	EL (%)	-18℃ (0°F)	-29℃ (-20°F)
SF-80W	550 (80,000)	620 (90,000)	26.5	82 (61)	40 (30)
AWS A5.29 E81T1-W2C	≥ 470 (68,000)	550~690 (80,000~ 100,000)	≥ 22.0	≥ 27J at -29℃ (≥ 20ft · lbs at -20°F)	

❖ Chemical Analysis of all weld metal(wt%)

Consumable	C	Si	Mn	P	S	Cu	Cr	Ni
SF-80W	0.04	0.42	0.95	0.016	0.009	0.41	0.50	0.52
AWS A5.29 E81T1-W2C	≤ 0.12	0.35~0.80	0.50~1.30	≤ 0.03	≤ 0.03	0.30~0.75	0.45~0.70	0.40~0.80


This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



Mechanical Properties & Chemical Composition of All Weld Metal

❖ Welding Conditions

Method by AWS Spec.

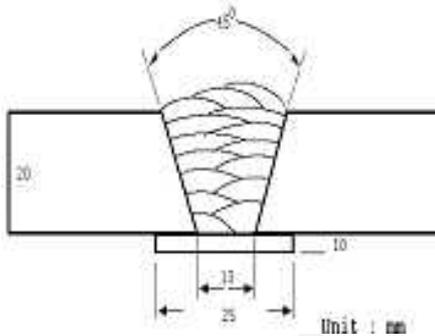

[Joint Preparation & Layer Details]

Welding Position	: 1G(PA)
Diameter	: 1.6mm (1/16in)
Shielding Gas	: 100%CO ₂
Flow Rate	: 20 ℓ /min
Amp./ Volt.	: 320~330A / 29~30V
Stick-Out	: 20~25mm (0.79~0.98in)
Pre-Heat	: R.T .
Interpass Temp.	: 150±15℃ (302±59°F)
Polarity	: DC(+)

❖ Mechanical Properties of all weld metal

Consumable	Tensile Test			CVN Impact Test J(ft · lbs)	
	YS MPa (lbs/in ²)	TS MPa (lbs/in ²)	EL (%)	-18℃ (0°F)	-29℃ (-20°F)
SF-80W	545 (79,000)	618 (90,000)	26.0	76 (56)	40 (30)
AWS A5.29 E81T1-W2C	≥ 470 (68,000)	550~690 (80,000~ 100,000)	≥ 22.0	≥ 27J at -29℃ (≥ 20ft · lbs at -20°F)	

❖ Chemical Analysis of all weld metal(wt%)

Consumable	C	Si	Mn	P	S	Cu	Cr	Ni
SF-80W	0.04	0.39	0.92	0.016	0.009	0.42	0.50	0.48
AWS A5.29 E81T1-W2C	≤ 0.12	0.35~0.80	0.50~1.30	≤ 0.03	≤ 0.03	0.30~0.75	0.45~0.70	0.40~0.80

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



Welding Efficiency

❖ Deposition Rate & Efficiency

Consumable (size)	Welding Conditions		Wire Feed Speed m/min (in/min)	Deposition Efficiency %	Deposition Rate kg/hr(lb/hr)
	Amp.(A)	Vol.t.(V)			
SF- 80W 1.2mm (0.045in)	200	26	10.2 (400)	84~87	3.4 (7.5)
	250	28	11.5 (450)	85~88	4.5 (9.9)
	300	33	15.3 (600)	86~88	5.2 (11.4)
SF- 80W 1.4mm (0.052in)	250	28	7.6 (300)	85~87	3.9 (8.6)
	300	32	10.2 (400)	85~88	4.8 (10.6)
	330	36	12.8 (500)	86~89	5.8 (12.8)
SF- 80W 1.6mm (1/16in)	280	31	6.4 (250)	85~88	4.2 (9.2)
	330	33	7.6 (300)	86~88	4.8 (10.6)
	350	34	8.1 (320)	87~89	5.3 (11.7)
	400	38	9.2 (360)	87~90	5.7 (12.5)
Remark				Deposition efficiency =(Deposited metal weight/ Wire weight used)×100	Deposition rate =(Deposited metal weight/ Welding time,min.)×60

* Shielding Gas : 100%CO₂

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



Diffusible Hydrogen Content

❖ Welding Conditions

Diameter	: 1.4mm (0.052in)	Amps(A) / Volts(V)	: 240A / 27V
Shielding Gas	: 100%CO ₂	Stick-Out	: 20~25mm (0.79~0.98in)
Flow Rate	: 20 l /min	Welding Speed	: 30 cm/min (12 in/min)
Welding Position	: 1G (PA)	Current Type & Polarity	: DC(+)

❖ Hydrogen Analysis Using Gas Chromatography Method

Hydrogen Evolution Time	: 72 hrs
Evolution Temp.	: 45 °C (113°F)
Barometric Pressure	: 780 mm-Hg

❖ Result(ml/100g Weld Metal)

X1	X2	X3	X4
6.5	6.3	6.2	6.6

Average Hydrogen Content 6.4 ml / 100g Weld Metal



Proper Welding Condition

❖ Proper Current Range

Consumable	Shielding Gas	Welding Position	Wire Dia.		
			1.2mm (0.045in)	1.4mm (0.052in)	1.6mm (1/16in)
SF-80W	100%CO ₂	F & HF	120~300Amp	200~350Amp	200~400Amp
		V-Up & OH	120~260Amp	180~280Amp	180~280mp
		V-Down	200~300Amp	220~320Amp	250~320Amp

❖ F No & A No

F No	A No
6	1

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.